

Product Specification

Product Model: Nickel-Cadmium Battery

Product Type: CD-SC2200P

Draw up: Technical Department

Date: 2008-10-15

AA Portable Portable Corp.

Web address : <http://www.batteryspace.com>

Tel:510-525 2328 Fax: 510-439-2808

E-Mail:sales@batteryspace.com

1 、 SCOPE

This specification governs the performance of the following Nickel-Cadmium cylindrical cell and its stack-up battery.

Model: CD-SC2200P

Cell Size: SC(22.0±0.1×42.0±0.5)mm

2 、 DATA OF STACK UP BATTERIES

All data involve voltage and weight of stack-up batteries are equal to the value of unit cell multiplied by the number of unit cell which consisted in the stack-up batteries.

Example : Stack-up batteries consisting three unit cells

Nominal voltage of unit cell=1.2V

Nominal voltage of stack-up batteries =1.2V×3=3.6V

3、 RATINGS

Description	Unit	Specification	Conditions
Nominal Voltage	V/cell	1.2	Unit cell or stack-up batteries
Nominal/Typical Cap	mAh	2000+/-5% / 2200	Standard Charge/Discharge
Standard Charge	mA	200 (0.1C)	T ₁ =20±5°C (see Note 1)
	hour	14~16	
Fast Charge	mA	1000 (0.5C)	- ΔV=0~15mV/cell , Timer Cutoff=120%nominal capacity , Temp.Cutoff=55°C, dT/dt=0.8°C/min, T ₁ =20±5°C
	hour	2.4 approx (see Note 2)	
Trickle Charge	mA	(0.03C)~(0.05C)	T ₁ =20±5°C
Standard discharge	mA	400 (0.2C)	T ₁ = 20±5°C Humidity: Max85%
Discharge Cut-off Voltage	V/cell	1.0	
Storage Temperature	°C	-20~30(Within 1 year)*	Discharged state
		-20~40(Within 6 months)	
		-20~50(Within 1 month)	
		-20~60(Within 1 week)	
Typical Weight	Gram	49 +/- 5	unit cell

*To keep the best performance for those not used for a long time,we recommend to charge and discharge the cells/batteries at least once in every 6 months.

4、 PERFORMANCE

Unless otherwise stated, tests should be done within one month of delivery under the following conditions:

Ambient Temperature : 20±5℃

Relative Humidity : 65±20%

Notes: Standard Charge/Discharge conditions:

Charge: 200 mA(0.1C)× 14 hours

Discharge: 400 mA(0.2C) to 1.0V/cell

Test	Unit	Specification	Condition	Remarks
Capacity	mAh	≥ 2000	Standard Charge / discharge	up to 3 cycles are allowed
Open Circuit Voltage(OCV)	V	≥ 1.25	Within 1 hour after standard charge	
Internal Impedance	mΩ	≤ 12	Upon fully charged(1KHz)	
High Rate Discharge(1C)	min	≥ 51	Standard Charge, 1 hour rest before discharge by 1C to	up to 3 cycles are allowed
Charge Retention	mAh	≥ 1300 (65%)	Standard Charge,Storage: 28 days,Standard Discharge	
IEC Cycle Life	Cycle	≥500	IEC61951-1(2003)7.4.1.1	see Note 3
Leakage		No leakage nor deformation	Fully charged 200 mA for 28 days	
Vibration Resistance		Change of voltage should be less than 0.02V/cell,change of impedance should be less than 5milliohm/cell	Charge the battery 0.1C 14hrs,then leave for 24hrs,check Battery before/after vibration,Amplitude 1.5mmVibration 3000 CPMAAny direction for 60mins.	
Impact Resistance		Change of voltage should be less than 0.02V/cell,change of impedance should be less than 5milliohm/cell	Charge the battery 0.1C 14hrsThen leave for 24hrs,check bat-before/ after dropped,Height 50 cm Wooden board(thickness 30mm) Direction not specified,3 times.	
Maximum continuous discharge current	A	20(10C)		
Maximum momentary discharge current	A	30		

5、 CONFIGURATION, DIMENSIONS AND MARKINGS

Please refer to the attached drawing.

6、 EXTERNAL APPEARANCE

The cell/battery shall be free from cracks, scars, breakage, rust, discoloration, leakage or deformation.

7、 WARRANTY

3 months limited warranty against workmanship and material defects.

8、 CAUTION

[1]Reverse charging is not acceptable.

[2]Charge before use. The cells/batteries are delivered in an uncharged state.

[3]Do not charge/discharge with more than our specified current.

[4]Do not short circuit the cell/battery Permanent damage to the cells/batteries may result.

[5]Do not incinerate or mutilate the cells/batteries.

[6]Do not solder directly to the cells/batteries.

[7]The expected life may be reduced if the cells/batteries are subjected to adverse conditions as:
extreme temperature, deep cycling, excessive overcharge/ over-discharge.

[8]Store the cells/batteries in a cool dry place. Always discharge batteries before packing.

Notes:

(1) T_1 : Ambient Temperature.

(2) Approximate charge time from discharged state, for reference only.


(3) IEC61951-1(2003)7.4.1.1 Cycle Life:

Cycle No.	Charge	Rest	Discharge
1	0.1C×16h	None	0.25C×2h20min
2-48	0.25C×3h10min	None	0.25C×2h20min
49	0.25C×3h10min	None	0.25C to 1.0V/cell
50	0.1C×16h	1-4h	0.2C to 1.0V/cell
Cycle 1 to 50 shall be repeated until the discharge duration on any 50th cycle becomes less than 3 h.			

CC'Rqt vcdng'Rqy gt 'Eqt r

MODEL No: CD-SC2200P

Description: 2200 mAh SIZE Ni-Cd SC

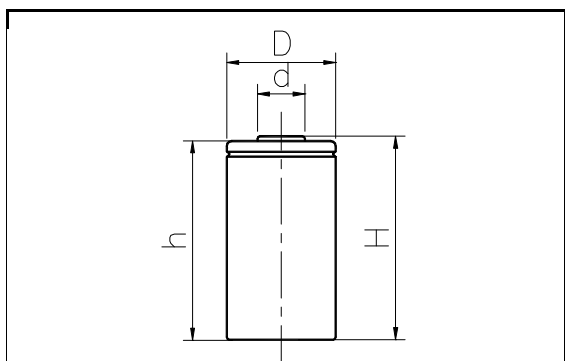

Dimensions(without Tube) (mm)

D	22.00 ± 0.10
d	10.00 ± 0.08
H	42.00 ± 0.50
h	41.50 ± 0.50

Specification

Nominal/Typical Capacity		2200/2000 mAh	
Nominal Voltage		1.2 V	
Charge current	Standard	200 mA	
	Fast	1000 mA	
Charge time	Standard	14~16 Hrs	
	Fast	2.4 Hrs	
Ambient Temperature	Charge	Standard	0°C~45°C
		Fast	10°C~45°C
	Discharge		-30°C~60°C
	Storage		-20°C~40°C
Internal Impedance(mΩ) (After Charge)		≤ 12	
Weight		49 g	

